Levelling and Sag Tester Model 419

Time-saving and practice-oriented testing method for determining the flow properties of coating materials



testing equipment for quality management



Technical Description and Operating Manual

	ASTM D 2801
	ASTM D 4400
	DIN 55 677

Testing principle

Parallel strips of wet film are applied to a substrate using a special paint applicator frame made of stainless steel and featuring slots of various heights.

The sag tendency is determined in a *vertical* flow test, the levelling tendency is ascertained when the specimen is *horizontal*. The specimen panel is examined visually after the coating has hardened.

Levelling and Sag Tester, Model 419-ASTM

Design and function

Slots are cut into two sides of the film applicator frame:

- The drawing blade for the levelling test features 5 pairs of slots (see fig. 1a). The slot widths, the span of each slot and the distance between the pairs of slots are predefined. The heights of the individual pairs of slots are graded in doubling steps ranging from 250 µm to 4 mm.
- The drawing blade for the sag test features 10 slots (see fig. 1b) which are graded in 25μm steps, increasing from 75 μm to 300 μm.

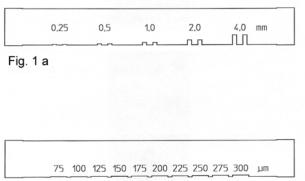


Fig. 1 b

Levelling test according to ASTM D 28011)

The wet film strips are applied to a predefined substrate using the doctor blade for levelling tests.

After the specimen has hardened in the horizontal position, the number of double strips which have merged with each other is established.

Sagging test according to ASTM D 4400

Method A

The strips of wet film are applied to a black-and-white contrast card²⁾ using the doctor blade of the applicator for sag tests (application rate approx. 150mm/s).

Immediately after application, the card is positioned vertically in such a way that the <u>strips</u> of film are horizontal, with the thinnest strip at the top.

After hardening, the level is determined which has not quite spread to the strip below. Further evaluation details are described in ASTM D 4400, Procedure A.

Method B

The strips of wet film are applied to a contrast card²⁾ as described in method A. Prior to application, however, two marking lines are drawn on the carton at right angles to the direction of application. 15 seconds after application the specimen is placed in a vertical position in such a way that the strips of film are vertical and the reference markings horizontal. After hardening, the level determined at which a shift of marking is just recognizable in relation to the original reference line. A detailed description is given in ASTM D 4400, Procedure B.

¹⁾ This standard was withdrawn in 1990

²⁾ Contrast cards, model 451, are suitable for this purpose.

Sag Tester, Model 419-DIN

Design

The four drawing blades of the film applicator frame feature a total of 24 slots (s. fig. 2). As in the case of Model 419-ASTM, the slot width and the distance between the slots is predetermined. The slot heights vary between 75 μ m and 1300 μ m.

Sag test according to DIN 55 677

The strips of wet film are applied, preferably to a standard specimen panel made of steel. Subsequent to application, the specimen panel is positioned vertically (film strips running across the panel with the thinnest strip uppermost) and the coating allowed to dry. A suitable thickness gauge is used to determine the thickness of the thickest layer where no change is evident as a result of sagging. This layer is regarded as the flow index for the sag properties.

шП	1300	1200	0011	0001	006	008		7
	75	100	125	150	175	200	шщ	

Fig. 2



Subject to technical modifications. Group 2 - TBE - I/00

Technical Data

Model 419-ASTM

Dimensions:

(L x H x W) 115 x 30 x 15 mm Net weight: approx. 0.1 kg

Thickness of drawing blade: 3 mm

Slot height:

Levelling test: 75 μm - 300 μm

(in 25-µm steps)

Sag test: 2 x each 250 μm, 500 μm,

1 mm, 2 mm and 4 mm

Slot width:

Levelling test: 6.4 mm

Sag test: 1.6 mm

Distance between slots:

Levelling test: 1.6 mm

Sag test: 2.5 mm (span of each slot pair)

12 mm (between the pairs of slots)

Model 419-DIN

Dimensions: 115 x 30 x 15 mm

Net weight: approx. 0.12 kg

Thickness of drawing blade: 5 mm

Slot heights: 75 µm - 300 µm

(in 25-μm steps) 350 μm - 700 μm (in 50-μm steps) 800 μm - 1300 μm (in 100-μm steps)

Slot width: 10 mm

Distance between slots: 2 mm

Ordering Information				
Order No.	Product Name			
0053.01.31	Levelling and Sag Tester Model 419-ASTM, incl. case			
0229.01.31	Sag Tester Model 419-DIN incl. case			

